

Analytical Summary

Data Collected & Analyzed By:

Northeast Laboratories, Inc
129 Mill Street
Berlin, CT 06037

Summarized & Commented By:

Bio-Tec Environmental
7009 Prospect Ave NE #202
Albuquerque, NM 87110

ASTM D 5511 – 02 Standard Test Method to Determine Anaerobic Biodegradation of Plastic Materials Under High-Solids Anaerobic-Digestion Conditions

The degree and rate of anaerobic biodegradability of a plastic type material may be predictive of the period required to reduce the proposed plastic from the environment depending on the given conditions. Where disposal is considered a major issue, this test method may be useful to estimate the degree and persistence of biodegradable plastic in a biologically active anaerobic disposal situation. ASTM method D5511-02 determines the degree of anaerobic biodegradation of plastic materials in a high-solids anaerobic conditions. The test sample is exposed to methanogenic inoculum cultivated from a wastewater treatment facility's anaerobic digesters operating on household waste. Anaerobic decomposition in this case employs a high solids environment. High solids conditions are usually considered to be greater than 20% solids. The sample conditions remain static.

This test method is designed to yield a percentage of conversion of carbon in the sample to carbon in the gaseous form under conditions found in high-solids anaerobic digesters, treating municipal solid waste. This can be validated using change in mass of the original sample. This test method is also designed to resemble many conditions in a biologically active landfill. This method is applicable to all plastic materials that are not toxic to microorganisms present in wastewater treatment facility's anaerobic digesters that are operating on household waste.

ASTM Method D5511 determines the rate and degree of anaerobic biodegradation by measuring the volume of carbon dioxide (CO₂) and methane (CH₄), or change in mass as a function of time (days) of exposure to anaerobic-digester sludge. This method is considered an accelerated representation with respect to anaerobic environments. Landfill sites that plastics encounter in usual disposal methods are a prime example of this environment.

Analytical Summary

Experiment:

1. Inoculum
 - 1.1. Isolation of an inoculum is the primary step.
 - 1.2. The dependability of the inoculum is determined by the positive control sample test.
 - 1.3. Sludge Characteristics and Preparation
 - 1.3.1. Sludge from Organic Compost – McEnroe Organic Farms, Millerton, NY
 - 1.3.2. Fifteen day hold period observed @ $53 \pm 2^\circ\text{C}$
 - 1.3.3. Solid Content - 24%
 - 1.3.4. pH - 7.9
 - 1.3.5. Volatile Fatty Acids - 0.9 g/kg
 - 1.3.6. Ammonium Nitrogen 1.3 mg/kg
2. Sample characteristics are observed and recorded.
 - 2.1. Carbon Content - 77.9
 - 2.2. Structure - Foam
 - 2.3. Sample Form – EVA Product
 - 2.4. Temperature Range During Study - $52 \pm 2^\circ\text{C}$
 - 2.5. Duration of study - 15 days
3. Experiment commences in an appropriate apparatus to verify gas evolution and sample isolation for final mass analysis.
 - 3.1. Incremental mass and gas evolution is measured for sample, control and positive control by considering mass loss.
 - 3.2. The experiment is continued for a given period of time.
 - 3.2.1. Fifteen days in this case.
 - 3.2.2. If gas production of actual sample reduces to that of the control sample the experiment is terminated.

Results:

After consideration of gas production of all samples, there appears to be no gross inconsistencies that would deem this experiment unusable. There is excellent continuity among the three samples.

	Average		Methane (CH ₄)			Carbon Dioxide (CO ₂)			Total Carbon (C)		Biodegradation	
	Wt (g)	Total Vol (ml)	%	Vol (ml)	Wt CH ₄ (g)	%	Vol (ml)	Wt (g)	Total Wt (g)	Theoretical (g), C _i	%	Adjusted %
Foam	49.9	33,175.0	50.3	16676	11.93	2.02	669	1.32	9.31	38.87	5.41	7.35
Positive	20.0	49,413.3	49.8	24624	17.62	1.98	980	1.93	13.74	8.88	73.59	100.00
Negative	99.5	25,691.7	49.8	12803	9.16	1.98	510	1.00	7.14	77.51	-0.08	-0.11
Inoculum	1000.0	25871.7	49.9	12919	9.24	1.97	509	1.00	7.21			


There was indication that the inoculum was viable, because the positive and sludge control results indicated biodegradation when gas production is considered.

Analytical Summary

As expected there was no biodegradation of the untreated (negative) control sample.

Conclusion & Analysis:

Upon consideration of gas production analysis, it becomes obvious that biodegradation has occurred. It appears that a linear curve is developing among all samples. It seems that the samples are continuing to accelerate in biodegradation.

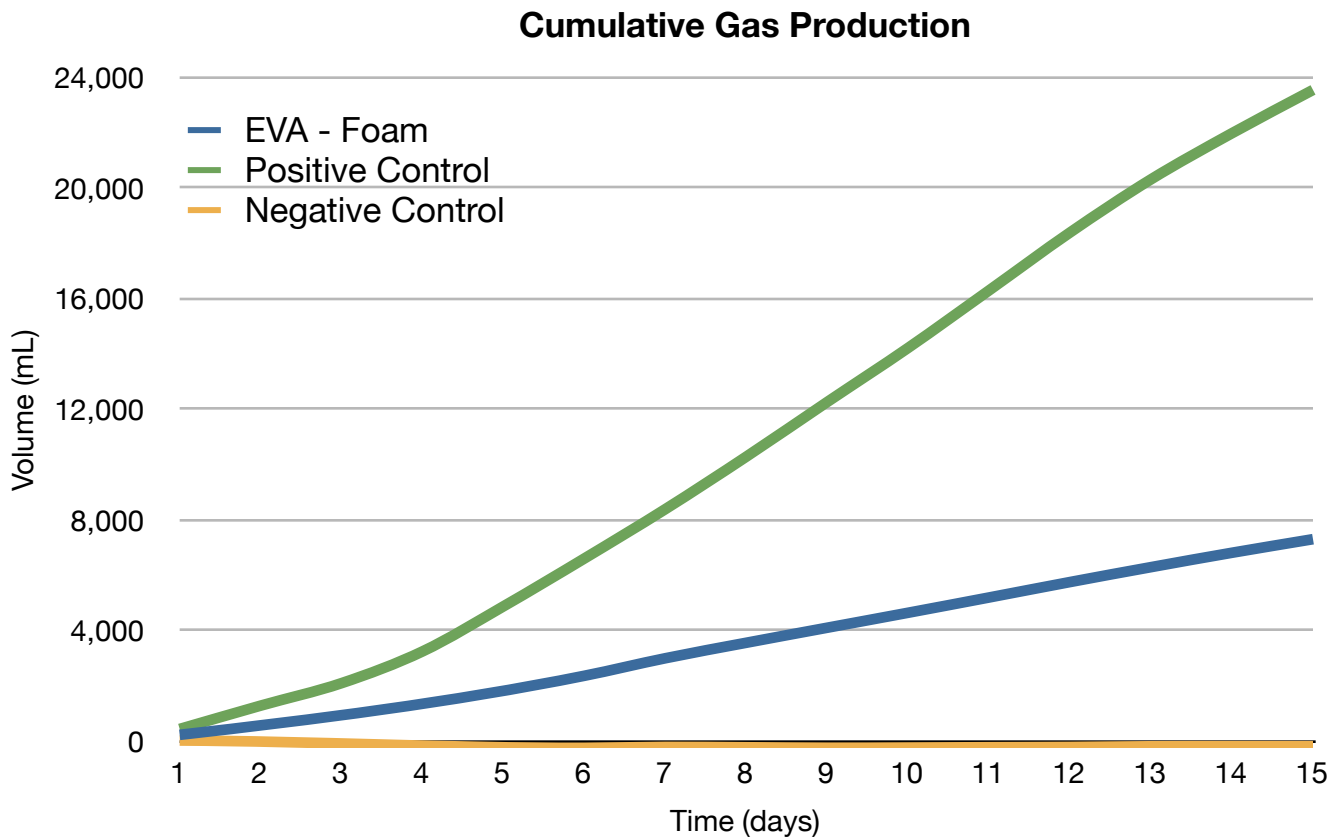

Prediction of time to total biodegradation is still difficult. It is unknown if the slope of biodegradation will remain linear for the majority of the degradation cycle. Over a 15 day period the sample showed over 5% biodegradation and as high as 7.35% when adjusted for the positive control.

These conditions are optimized. These results are very good. If your products were disposed of in a bioreactor landfill the biodegradation rate would be very fast. In this test, temperature and moisture are optimized as in a bioreactor. In a standard landfill these parameters are not optimized so biodegradation would not be as accelerated. To determine an accurate time to total degradation additional testing would be required. This will be further addressed in the final summary.